

PREPARATION OF SPHERICAL POLYMERIC PARTICLES FROM TANZANIAN CASHEW NUT SHELL LIQUID BY SUSPENSION POLYMERIZATION

LL Mkayula, YMM Makame and TH Matechi
Department of Chemistry, University of Dar es Salaam,
P.O. Box 35061, Dar es Salaam, Tanzania

Accepted 04 March 2004

ABSTRACT


Spherical Polymeric Particles (SPP) have been prepared from Tanzanian Cashew Nut Shell Liquid (CNSL) by suspension polymerization technique involving either step-growth or chain-growth polymerization mechanisms. The sizes of the SPP, which ranged from 0.1 to 2.0 mm were strongly influenced by the amounts of stabilizers in polymerization recipes used. The particles showed variable surface areas, indicative of the presence of pores in some of the preparations and the highest surface area recorded was about 260 m²g⁻¹. The particles were found to exhibit Langmuir-type adsorption isotherms with saturation capacity of about 9.0 and 44.2 mg/g for Na⁺ and Ca²⁺, respectively. Step-growth polymerization produced SPP with relatively smaller surface areas and lower adsorption capacities of sodium and calcium ions compared to the particles produced through the chain-growth mechanism. Other particle characteristics depended strongly on the recipe employed and the surface OH functional groups apparently determine the potential applications of the SPP.

INTRODUCTION

Preparation of spherical polymeric particles by suspension polymerization technique is well documented (Mark et al. 1989, Ahmed 1984, Brooks 1990). The sizes of the polymer particles resulting from suspension polymerization range between about 50 μ m and 5 mm hence the term bead or pearl polymerization. Spherical polymeric particles have been used in a wide range of surface-chemical applications, such as support for catalysts (Arshady 1992, Hodge 1980), gel filtration and ion exchange resins (Rolls et al. 1990). These particles are suited for such applications due to their mechanical stability, narrow size distribution and dynamic behavior as well as the ease with which mathematical modeling of chemical processes can be worked out (Mark et al. 1989).

Recently the synthesis of polymers from renewable natural resources has attracted

considerable attention of research workers due to escalating prices as well as high rate of depletion of the natural mineral resources (Bhunia et al. 1998, Mwaikambo and Ansell 2001). Cashew Nut Shell Liquid (CNSL) is a natural product whose source is the cashew tree, *Anacardium occidentale* Lin, which is a widely grown cash crop in Tanzania and in some neighboring countries. The industrial process of recovering edible kernel from the nuts yields, as a by-product, the technically useful reddish brown CNSL (Anand 1978, Gedam et al. 1986). Chemical analyses of CNSL have established that the liquid consists of a mixture of phenolic compounds having long chains of saturated and unsaturated hydrocarbon substituents and consists of mainly four major components, namely, cardanol (**1**), cardol (**2**), 2-methyl cardol (**3**) and anacardic acid (**4**).

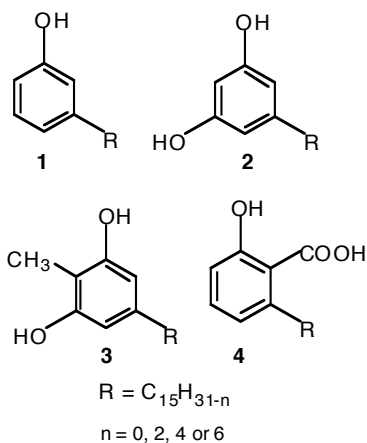

Cardanol is present in small amounts in solvent extracted CNSL but it is the major product of thermally extracted CNSL (Tyman 1975).

As a result of the phenolic nature and the presence of the long alkyl chain with a variable degree of unsaturation, the components of CNSL have been subjected to step-growth polymerization or chain-growth polymerization to yield numerous polymer products for various applications such as surface coating, adhesives, laminating resins, friction resistant components, molding materials, surface active agents, oil and paint additives, and ion-exchange resins or membranes (Anand 1978, Anand 1981, Gedam et al. 1986). The manufacture and application of CNSL based polymers, however, are reported in the patent literature, if not kept as industrial secrets.

Although workers in many industrial laboratories have attempted to polymerize CNSL under different experimental conditions, very little has been reported at on suspension polymerization of the same, to produce surface reactive materials. In this work, suspension polymerization of CNSL and its distillate product cardanol to produce spherical polymeric particles (SPP) and

surface characterization of the latter is reported.

EXPERIMENTAL

Materials

Technical CNSL was supplied by TANITA Company Limited based in Dar es Salaam. Pure cardanol was obtained by vacuum distillation of CNSL at 180 °C and 0.1 mmHg and its purity was affirmed by TLC. All reagents and solvents were A.R. grade supplied by Aldrich. White spot nitrogen gas and liquid nitrogen were supplied by Tanzania Oxygen limited (TOL).

Preparation of Spherical Polymeric Particles

Suspension polymerization was carried out in a four-neck jacketed reactor of 1 dm³ capacity with water as the dispersion medium and either CNSL or cardanol in the dispersed monomer phase. The reactor was equipped with a glass baffle, a teflon stirrer, a nitrogen gas inlet tube, a thermometer and a J-shaped glass tube for sampling.

For the chain-growth (addition) polymerization of CNSL or cardanol, the predetermined volume of distilled water and the respective amounts of stabilizers (as shown in table 1) were charged into the reactor and the mixture was heated under nitrogen purging. In a separate container, the initiator was dissolved in either the technical CNSL or the freshly distilled cardanol and later added into the reactor after the latter's contents had attained the chosen reaction temperature.

In step-growth (condensation) polymerization of CNSL or cardanol, the reactor was charged with a mixture of distilled water and stabilizers followed by heating under nitrogen purging. A mixture of either CNSL or its distillate and formalin with 2 – 3 ml of 7% sodium hydroxide was mixed with the aqueous mixture after the latter had attained the reaction temperature. The exact amounts of ingredients used are shown in table 1.

Constant temperature and agitation were maintained throughout the period of polymerization. The particles formed were separated from the reaction medium by using basket sieves, washed with plenty of distilled water and dried in a Gallenkamp oven at between 80 and 150 °C overnight.

Determination of Chemical Stability of the Particle

The CNSL based spherical polymer particles were treated with different reagents including organic solvents, mineral acids and concentrated alkaline solutions in order to determine their resistance against chemicals and solvents. The particles were soaked in different reagents for 24 to 48 hours and subsequently observed for any change in their physical structures, physico-chemical properties as well as attrition.

Determination of Particle Sizes

Standard testing sieves (specification E 11 ASTM) were used for particle size analyses. The dried SPP samples were shaken for 20 min by an EML 200 – 67 vibration machine at a vibrating amplitude of 60.

Determination of Surface Area

The surface areas of the beads were determined from nitrogen physical adsorption measurements carried out at 77 K in a static volumetric adsorption system as reported elsewhere (Heal and Mkayula 1988). The surface areas were evaluated from N₂ adsorption data using the BET equation (Brunauer et al. 1938).

Determination of Ion Adsorption Capacity

The ion adsorption capacity of the SPP was determined by batch method as follows: 200 ppm stock solutions of Na⁺ and Ca²⁺ were prepared by dissolving appropriate amount of a pure carbonate of the respective metals in small amount of dilute hydrochloric acid, followed by dilution with distilled water to the required volume. Less concentrated solutions of sodium and calcium ions were obtained by successive

dilution of the stock solutions with distilled water. Samples of polymer beads weighing about 0.1 g were placed in Erlenmeyer flasks and mixed with solutions of different concentrations of sodium or calcium ions. The flasks were then placed on a batch shaker and shaken at a rate of 130 strokes/min at 25 – 30 °C for 24 hours. Thereafter the beads were filtered-off and the concentrations of both the treated and untreated solutions were determined by Atomic Absorption Spectroscopy (AAS). A Perkin-Elmer spectrometer model AA-300 was used.

RESULTS AND DISCUSSION

Preparation of SPP

Vacuum distillation of CNSL gave cardanol fraction of 98% purity and yield of about 42%. Cardanol was used as a monomer in some of the recipes, in other recipes the technical CNSL was used without further purification. Table 1 shows various successful recipes for preparing SSP. The recipes involved cardanol (CDN), a mixture of styrene and cardanol (SCDN), and technical cashew nut shell liquid (CNSL). The SSP produced were coded in such a way that the abbreviation before a bracket represents the monomer used; the number inside the bracket represented the recipe number; and the abbreviation C_gP or S_gP after the bracket describes the most likely polymerization mechanism involved in the given recipe. Generally longer reaction times (12 – 24 h) were required to obtain SPP by addition (chain) polymerization compared to 6 – 10 h needed to get SPP by condensation (step) polymerization under similar conditions of temperature. This difference in rates between the step-growth and chain-growth polymerization of CNSL or its distillation product, cardanol, is not unexpected and could be attributed to the differences in the kinetics of the reaction mechanisms involved. Though SPP were obtained much faster by step growth mechanism, stabilization of the particles in this case required larger amounts of stabilizers than by chain growth mechanism.

Table 1: Preparation of spherical polymeric particles – the successful recipes.

Recipe no.	Amounts of different ingredients in the recipes				Reaction Temp.(°C)
	Monomer System	Initiator /catalyst	Water (g)	Stabiliser system	
CNSL[12]S _g P	CNSL = 10.0 g formalin = 5 ml	7% NaOH = 2 ml	600	Mg(OH) ₂ = 1 g Ca ₃ (PO ₄) ₂ = 1 g	30
CDN[17]C _g P	cardanol = 5 g	(CH ₃) ₂ SO ₄ = 3 ml	650	Mg(OH) ₂ = 0.5 g Ca ₃ (PO ₄) ₂ = 0.5 g	50
CDN[18]C _g P	cardanol = 5 g	B.P = 0.5 g	350	Starch = 2 g	30
SCDN[21]C _g P	styrene = 2.5 g cardanol = 2.5 g	B.P = 0.1 g	300	Ca ₃ (PO ₄) ₂ = 2 g Mg(OH) ₂ = 1 g Al(OH) ₃ = 0.5 g	40
CNSL[23]C _g P	CNSL = 10 g	B.P = 0.15 g	400	Starch = 2 g Ca ₃ (PO ₄) ₂ = 0.5 g	55
CNSL[27]S _g P	CNSL = 5 g formalin = 3 ml	7% NaOH = 2 ml	600	Mg(OH) ₂ = 1.5 g	50
CNSL[29]S _g P	CNSL = 10 g formalin = 5 ml	7% NaOH = 3 ml	650	Ca ₃ (PO ₄) ₂ = 2 g Mg(OH) ₂ = 1.5 g Al(OH) ₃ = 0.5 g	45
CNSL[37]C _g P	CNSL = 12.7 g	B.P = 2.53 g	500	Ca ₃ (PO ₄) ₂ = 2 g Mg(OH) ₂ = 1 g Starch = 1.5 g	60
CDN[38]C _g P	cardanol = 5.8 g	B.P = 0.43 g	400	Ca ₃ (PO ₄) ₂ = 2.5 g Al(OH) ₃ = 1 g Starch = 1.3 g	60
CNSL[40] S _g P	CNSL = 10 g formalin = 10 ml	7% NaOH = 3 ml	600	Mg(OH) ₂ = 1 g BaSO ₄ = 0.5 g	55

B.P = Benzoyl peroxide; in each recipe 2-3 ml of dodecyl alcohol was added as a porogen

During SPP preparation, it was noted that use of large volume of monomer in the recipe relative to the volume of the aqueous phase changed the polymerization course to bulk polymerization. In such situations, (recipes no. 6, 7, 8, 11 and 20, - not shown in Table 1), the agitation mechanism could not effectively disperse the monomer phase into droplets and the stabilizer system consequently failed to prevent coalescence of the monomer phase.

Most of the unsuccessful recipes were those involving chain-growth mechanism, i.e., those in which benzoyl peroxide was used as the initiator. It was observed that with the amount of benzoyl peroxide less than about 1.5 % the weight of the monomer, polymerization could not proceed for

sufficient period of time thereby leading to coagulation and failure to SPP formation.

Chemical Stability of SPP

The results of treatment of SPP with reactive agents are given in Table 2. The results indicate that SPP have good resistance against chemical attack of many common solvents. When treated with concentrated sodium hydroxide solution and most of organic solvents, the particles remained physically stable and maintained mechanical integrity. Most of the solvents, however, extracted color from the polymer particles but the particles remained undestroyed. The treatment with concentrated sulphuric acid, on the other hand, seemed to dehydrate and carbonize the particles. Heating the particles to 120 – 150 °C, like treatment with mineral acids, resulted in improved hardness of the

particles. The fact that the particles were largely unaffected by harsh chemical environment and remained stable, suggests

the plausibility of using SSP for catalyst supports and other surface-active applications.

Table 2: The effect of treatment of SPP with various chemical agents

Reagents	CNSL[12]S _g P	CNSL[29]S _g P	CNSL[23]C _g P	CNSL[37]C _g P dried - 80°C	CNSL[37]C _g P dried -140°C
Methanol	Bleached	No effect	No effect	Corroded	No effect
Ethanol	No effect	No effect	No effect	No effect	No effect
Chloroform	Bleached, Corroded	Swollen	No effect	Corroded	No effect
Ethyl acetate	Swollen	Swollen	No effect	No effect	No effect
n-Hexane	No effect	Swollen	No effect	Corroded	No effect
97% H ₂ SO ₄	Carbonized, Hardened	Carbonized, Hardened	No effect	Carbonized, Hardened	No effect
dil H ₂ SO ₄	No effect	No effect	No effect	No effect	No effect
conc HNO ₃	Bleached, Hardened	Bleached, Hardened	No effect	Bleached	No effect
5M NaOH	No effect	No effect	No effect	Swollen	No effect
conc H ₃ PO ₄	No effect	No effect	No effect	No effect	No effect

The Average Particle Size of SPP

The SEM picture of the SPP obtained from recipe CNSL[40]S_gP is shown in Figure 1. Apparently the particles obtained have narrow size distribution. A highly magnified micrograph of a single polymer particle (Figure 2) enables a closer examination of the morphology of the particles. From figure 2, the spherical shape of the particle is evident.

The particle seems to have smooth surface with craters. These craters are probably due to the small stabilizer particles that are lightly adsorbed on the polymer particle surface during the polymerization reaction. After the reaction these stabilizer particles are washed off but leave their imprints on the surface in the form of craters.

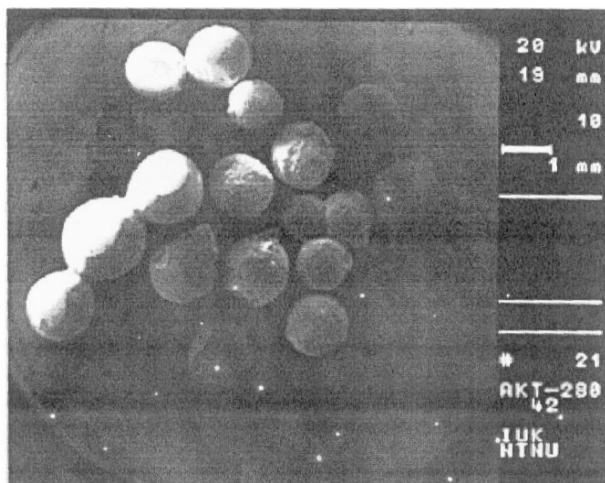


Figure 1: Spherical polymer particles from CNSL.

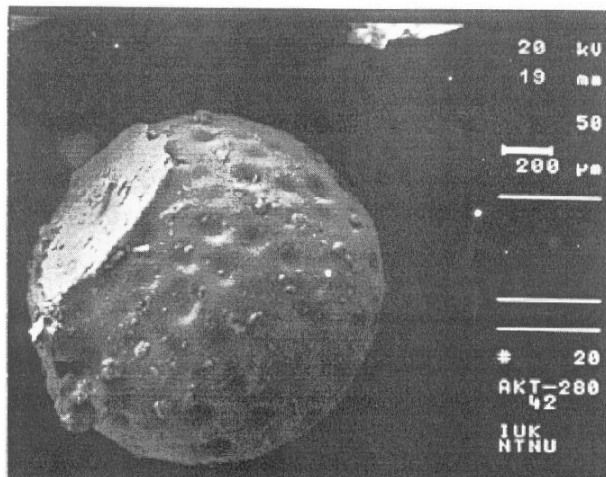


Figure 2: A magnified polymer particle from CNSL

Typical results of particle size analysis are depicted in Figure 3, which gives the size distribution for SPP from recipe no. CNSL[12]S_gP. The modal size and the

average size of the particles from this recipe are 0.7 mm and 0.9 mm, respectively. The sizes of the particles obtained from other recipes are summarized in Table 3.

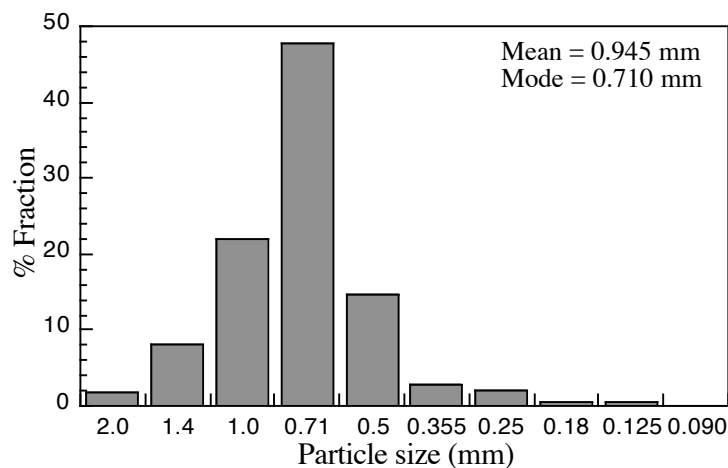


Figure3: Size distribution for spherical polymer particles obtained from recipe no. CNSL[12]S_gP.

The average particle sizes of polymer beads prepared by suspension polymerization are known to depend on both the strength of agitation (Ahmed 1984, Brooks 1990) and the nature and concentration of stabilizers

employed (Landall 1982, Wright 1985). In this case a constant agitation speed was maintained. However, the effect of concentration of the stabilizer on the average particle size is apparent. The average particle

sizes decreased with increasing amount of stabilizers in the recipes. This is the expected observation since the more the stabilizer the larger the surface area that can be stabilized. By varying the concentrations of stabilizers

in different recipes, SPP particles with average sizes ranging from 0.4 to 1.6 mm, with a maximum and minimum sizes of 2.0 and 0.1 mm, respectively, could be obtained.

Table 3: A summary of particle size analysis of SPP.

Recipe no.	Size (diameter) of SPP	
	Modal size (mm)	Average size (mm)
CNSL[12]S _g P	0.7	0.95
CDN[17]C _g P	1.0	0.91
CDN[18]C _g P	0.5	0.73
CNSL[23]C _g P	0.7	0.64
CNSL[27]S _g P	2.0	1.47
CNSL[29]S _g P	0.25	0.42
CNSL[37]C _g P	1.6	1.2
CDN[38]C _g P	0.25	0.39
CNSL[40]S _g P	1.2	1.19

Particles Surface Area

From Table 4, it can be seen that the beads prepared without a porogen have smaller surface areas than those prepared with the porogen. For example, in recipe 5 and 29 the surface area changed from 1.3906 (recipe 5) to 15.676 m²g⁻¹ (recipe 29). It appears that the increase in surface area is caused by the added porogen in a manner that still remains equivocal. Indeed this is evidence of the porogen (pore-generating agent) at work, i.e., developing the pore system of the beads

and thus affecting their internal surface area. Furthermore, it is noted that beads prepared from CDN have larger surface areas than beads prepared from CNSL (table 2, recipe 18 and 23). Generally it is noted that beads prepared via a chain-growth polymerization mechanism had larger surface areas than those prepared by step-growth polymerization. However, further work is needed to establish and account for the observed differences.

Table 4: Surface area values for some of the SPP prepared.

Particle Recipe code	Weight of sample (g)	Degassing Temp. (°C)	Degassing Time (h)	S _{BET} (m ² /g)
CNSL[5]S _g P	0.046	200	12	1.4
CDN[17]C _g P	0.061	250	18	4.6
CDN[18]C _g P	0.085	250	12	260
CNSL[23]C _g P	0.050	250	12	83
CNSL[29]S _g P	0.098	250	18	16
CNSL[38]C _g P	0.052	200	18	110

Adsorption Capacity

The adsorption capacity of the SPP was determined by the batch technique using Na⁺ and Ca²⁺ adsorbates. The results were interpreted by the Langmuir equation whose plots are shown in Figures 4 and 5. The

plots show the amounts of adsorbate adsorbed in mg/g versus the electrolyte concentration. At the concentration of about 50 mg/dm³ of Na⁺, CDN[18]C_gP adsorbed 7.43 mg/g and CDN [17]C_gP adsorbed 2.49 mg/g. But CNSL[5]S_gP adsorbed 8.34

mg/g of Ca^{2+} whereas CDN[38]CgP adsorbed 26.87 mg/g of Ca^{2+} . This implies that the adsorption increased with the increase in surface area. According to the results, the adsorption characteristics of the SPP conform to the Langmuir adsorption isotherm (Langmuir 1916) with maximum

saturation capacity of about 9.0 mg/g and 44.2 mg/gram for Na^+ and Ca^{2+} , ions respectively. The higher affinities of CNSL resins for bivalent cations compared to univalent cations at low concentrations have been reported previously (Gedam et al. 1986).

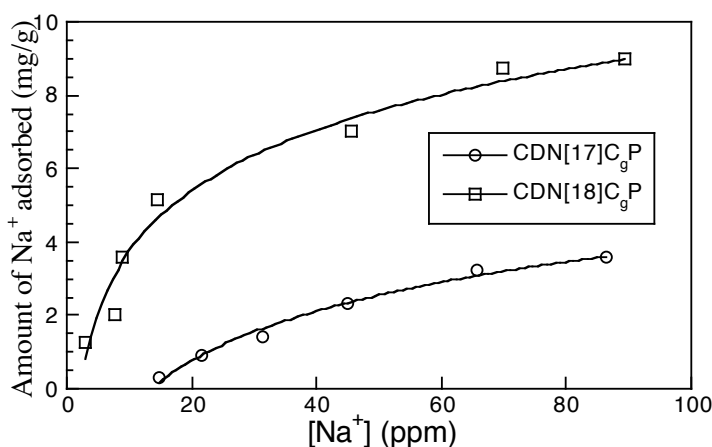


Figure 4: Adsorption of Na^+ by SPP.

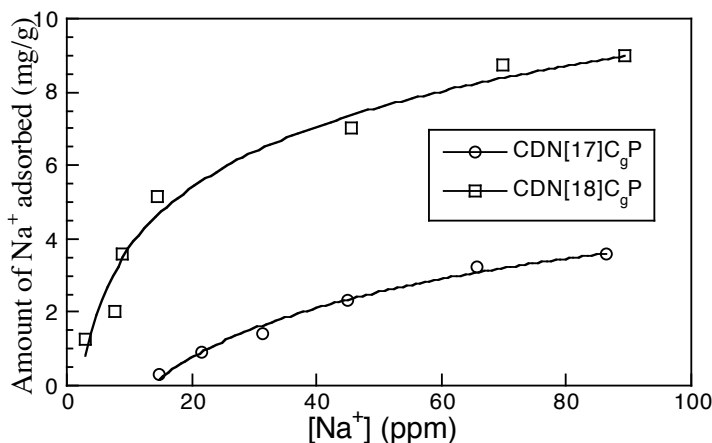


Figure 5: Adsorption of Ca^{2+} by SPP.

CONCLUSION

This study establishes that it is possible to prepare spherical polymeric particles from CNSL and its distillate, cardanol, by suspension polymerization. The strong

influence of amount of stabilizers on the size of the polymer particles is observed. It is further observed that the particles formed can be used for adsorbing cations, particularly the particles prepared from cardanol by

addition polymerization. Further study is in progress to establish the effect of different porogens, at various concentrations, to the surface area of the particles. The particles themselves are being investigated for their application as precursors of functionalized catalysts utilizing the surface hydroxyl groups.

ACKNOWLEDGEMENT

We are grateful to the Norwegian Agency for Development Cooperation (NORAD), through the Chemistry Department, University of Dar es Salaam for financing this project.

REFERENCES

- Ahmed SM 1984 Effect of agitation and the nature of protective colloid on particle size during suspension polymerization *J. Disp. Sci. Technol.*, **5**: 421-432.
- Anand LC 1978 CNSL based polymers and their applications *Paintindia* **28**: 13 - 33.
- Anand LC 1981 Some reaction of CNSL and its constituents, *J. Chem. & Petrochem.*, **12**(5): 1.
- Arshady R 1992 Suspension, emulsion and dispersion polymerization: A methodological survey *Colloid. Polym. Sci.* **270**: 717 - 732.
- Bhunia HP, Jana RN, Basak A, Lenka S and Nando GB 1998 Synthesis of polyurethane from Cashew Nut Shell Liquid (CNSL), a renewable resource *J. Polym. Sci. Part A: Polym. Chem.* **36**: 391 - 400.
- Brooks BW 1990 Basic aspects and recent development in suspension polymerization *Makromol. Chem., Macromol. Symp.* **35/36**: 121-140.
- Brunauer S, Emmett PH and Teller E 1938 Adsorption of gases in multimolecular layers. *J. Am. Chem. Soc.*, **60**: 309 - 319.
- Gedam PH and Sampathkumaran PS 1986 Cashew Nut Shell Liquid: extraction, chemistry and applications *Prog. Org. Coatings*, **14**: 115 -157.
- Heal GR and Mkyula LL 1988 The preparation of palladium metal catalysts supported on carbon: Part I - Selection and treatment of carbons *Carbon*, **26**: 803 - 813.
- Hodge P and Sherrington DC 1980 Polymer-Supported reactions in organic synthesis, John Wiley and Sons.
- Landall LM (Hercules Inc.) 1982 Use of hydrophobically modified water soluble polymers in suspension polymerization. US. Pat. 4,352,916.
- Langmuir I 1916 Kinetic model of the adsorption process *J. Amer. Chem. Soc.* **38**: 222.
- Mark HF, Bikales NM, Overberger CG, and Menges G 1989 Suspension polymerization *Encyclopedia of Polymer Science and Engineering*, 2nd ed., Wiley; **16**: 443 - 471.
- Mwaikambo LY and Ansell MP (2001) Cure characteristics of alkali catalysed cashew nut shell liquid-formaldehyde resins. *J. Materials Sci.* **36**: 3693 - 3698.
- Tyman JHP 1975 Long-chain phenols: V. Gas chromatographic analysis of cashew nut shell liquid (anacardium occidentale) *J. Chromatogr.* **111**: 285 - 292.
- Rolls W, Svec F and Frechet JMJ 1990 Design and synthesis of macroporous polymeric separation media based on substituted phenols, *Polymer*, **31**: 165 -174.
- Wright HA 1985 (Atlantic Richfield Co.) Process for bead size control in vinyl aromatic suspension polymerization using sodium polystyrenesulphonate. US. Pat. 4,500,692.

