

EFFECTS OF TARGET COMPOSITION ON THE OPTICAL CONSTANTS OF DC SPUTTERED ZnO:Al THIN FILMS

B. Samwel* M. E. Samiji and N.R. Mlyuka,

Solar Energy Group, Physics Department,
University of Dar es Salaam,
P. O. Box 35063 Dar es Salaam, Tanzania.

*College of Natural and Mathematical Sciences,
Physics Department, University of Dodoma,
P. O. Box 338, Dodoma, Tanzania

Emails: (N.R. Mlyuka) nmlyuka@yahoo.com

ABSTRACT

Al-doped ZnO thin films were deposited from ZnO:Al ceramic and Zn:Al metal alloy targets in Ar and Ar + O₂ atmospheres respectively, using Direct Current (DC) magnetron sputtering. The samples exhibited transmittance $T > 80\%$ in visible region with good NIR shielding. The results indicated that, band gap energy ranged from 3.34 to 3.44 eV and 3.39 to 3.46 eV for films prepared from alloy and ceramic targets, respectively. Films obtained from alloy target at a substrate temperature of 200 °C showed low electrical sheet resistance of 10 Ω/sq, and highest values of mobility (15.9 cm²/Vs) and carrier concentration (2.98×10^{21} cm⁻³). However, films prepared from ceramic target at a substrate temperature of 300 °C revealed the highest sheet resistance of 32 Ω/sq, with lower values of mobility (14.1 cm²/Vs) and carrier concentration (1.92×10^{20} cm⁻³). The increase in sheet resistance and decrease in mobility as well as carrier concentration might be due to increased scattering centers for carriers, resulting to increased sheet resistance. Optical spectra of the films were fitted to SCOUT software in order to determine the refractive index, n and extinction coefficient, k . Generally, the calculated n and k in the visible part of the solar spectrum for different samples, ranged from 1.59 to 2.2 and 0.00013 to 0.0194 respectively, which are in agreement with results obtained using other methods. In general, the findings of this study shows that alloy target is suitable for deposition of ZnO:Al thin films for devices/applications where low deposition temperature is required.

Key words: DC Magnetron Sputtering, Optical Constants, Transparent Conducting Oxides (TCO)

1.0. INTRODUCTION

Al doped zinc oxide films (ZnO:Al) are wide-band-gap semiconductors with high visible transparency, high reflectance in the near infrared (NIR) wavelength along with good electrical conductivity of nearly semi-metallic regime. The combination of high visible transparency with good electrical conductivity makes ZnO:Al films widely applicable for

potential application in optoelectronic devices where either optical, or electrical properties or both are used (Minami *et al.* 1985, Schaefer 1997, Granqvist 2007, Li *et al.* 2012). However, ZnO:Al properties are highly dependent on defect structure, deposition technique and the deposition parameters employed. Film thickness and substrates used can also have great influence

on the properties (Sittinger *et al.* 2010, Reddy *et al.* 2012).

ZnO:Al films has recently gained much attention as a promising alternative material to tin oxide (SnO₂), indium oxide (In₂O₃) and indium- or fluorine-doped SnO₂ because of its competitive electrical and optical properties as well as availability in natural resource an being a low-cost material (Kim *et al.* 2007, Ehrmann and Reineke-Koch 2010, Kuo *et al.* 2012). Apart from that, ZnO has good chemical stability in hydrogen plasma, for example in silane (SiH₄) which is used for the preparation of a-Si:H thin film solar cells (Beyer *et al.* 2007, Huang *et al.* 2011). Moreover, it has been reported that ZnO:Al films have good roughening and surface texturing which helps to enhance light scattering and absorption inside a solar cell and thus enhance the performance of a solar cell (Beyer 2007).

Various deposition techniques have been employed in preparing ZnO:Al films. Besides chemical vapour deposition (CVD), spray pyrolysis, pulsed laser deposition and sol-gel, magnetron sputtering is widely used (Wang *et al.* 2009, Fernández and Naranjo 2010, Sittinger *et al.*, 2010, Hwang *et al.* 2011, Alnajjar 2012). This technique allows deposition of ZnO:Al films at low substrate temperatures down to room temperature and at high deposition rates. The sputtered films show good adhesion on substrates and the technique offers very good thickness uniformity and high density of the films (Hwang *et al.* 2011, Alnajjar 2012). Taking this into account, magnetron sputtering is considered as a favourable deposition technique in which ZnO:Al films with good optical properties can be deposited.

Among the factors that influence physical properties of DC sputtered ZnO:Al thin films are

the target composition and deposition parameters used. It was reported that, using metallic Zn:Al targets in preparing sputtered ZnO:Al resulted in high quality films with good physical properties (May *et al.* 2003, Hong *et al.* 2003, Sucheai *et al.* 2007, Sittinger 2009). Other literatures, (Wang 2009, Huang *et al.* 2011) reported that high quality ZnO:Al thin films with good physical properties were obtained by preparing the films from ceramic targets. In the present work, investigations on the effect of target composition (ceramic against metallic targets) on the optical constant of ZnO:Al thin films have been carried in order to identify the suitable type of target for the preparation of good DC sputtered ZnO:Al thin films for solar cell applications.

2.0. MATERIALS AND METHODS

2.1. SAMPLE PREPARATION

ZnO:Al films were deposited on soda lime glass (SLG) substrates by reactive DC magnetron sputtering using BALZER BAE 250 coating unit. DC magnetron sputtering using metallic targets consisting of a Zn:Al alloy (2% Al) and ceramic target containing ZnO:Al (2% Al) (both from AJA International Inc., USA) were employed. The sputtering chamber was pumped down to a base pressure of 4.3×10^{-6} mbar using a turbo-molecular pump backed by a rotary pump. The sputtering gas (Ar 99.999%) and reactive gas (O₂ 99.999% purity) were introduced into the chamber separately, and were controlled through the gas mass flow rate controllers. The gas flow meters were controlled precisely to allow flow rates of oxygen and argon gases at about 5.0 – 5.5 and 60 ml/min, respectively for the case of Zn:Al target. However, for ceramic target ZnO:Al, oxygen and argon gases flow rates were at about 0 ml/min and 10 – 70 ml/min, respectively. The substrate temperature was varied from 100 °C to 350 °C, however, in this study, the optimal values of substrate

temperatures were 200 °C and 300 °C for films prepared from alloy and ceramic targets, respectively. The sputtering power of 70 W was used and pre-sputtering for 10 minutes was made so as to make the plasma stable and Target to substrate distance was fixed at 15 cm for both targets.

2.2. CHARACTERIZATION TECHNIQUES

The computerized, high sensitivity surface profiler, Alpha step IQ Surface profiler was used to measure the thickness of ZnO:Al films. A small portion at the edge of the substrate was covered using adhesive Teflontape before deposition so as to create a step for measuring the film thickness. X-ray diffractometer with $\theta-2\theta$ scanning mode was used for crystalline characterization. The diffraction angle (2θ) was varied from 5.000o to 84.997o. The electrical properties were investigated using a Hall Effect Measurement System (Ecopia HMS 3000) connected to the computer for displaying electrical properties. The optical transmittance and reflectance in the UV/VIS/NIR was measured in the wavelength range of 250 - 3000 nm at an interval of 1 nm by using Shimadzu SolidSpec-3700 DUV Spectrophotometer.

Optical spectra of the films were fitted to SCOUT software (Theiss 2008) in order to determine the refractive index, n and extinction coefficient, k , whereby three layers; air, ZnO:Al and substrate were theoretically implemented. The classical Drudemodel was used in which the fundamental quantity describing the dielectric response of any material is the complex dielectric function related to the complex refractive index as shown by equation 1.

$$\tilde{n} = n(\lambda) + ik(\lambda) = \sqrt{\varepsilon_{re} + i\varepsilon_{im}} \quad (1)$$

where \tilde{n} is the complex refractive index, $n(\lambda)$ refractive index and $k(\lambda)$ extinction coefficient.

The real (ε_{re}) and imaginary parts ($i\varepsilon_{im}$) of the dielectric function are related to the optical constants (n and k) by equation 2 and 3 (Hamberg and Granqvist, 1986);

$$\varepsilon_{re} = n^2 - k^2 = \varepsilon_{\infty} \left(1 - \frac{\omega_p^2}{\omega^2 + \Gamma^2} \right) \quad (2)$$

$$\varepsilon_{im} = 2nk = \varepsilon_{\infty} \frac{\Gamma}{\omega} \left(\frac{\omega_p^2}{\omega^2 + \Gamma^2} \right) \quad (3)$$

Where ω_p is the plasma frequency, Γ is the damping constant and ε_{∞} is the high frequency dielectric constant.

3.0. RESULTS AND DISCUSSION

3.1. STRUCTURAL CHARACTERISATION

The crystalline structure and orientation of the ZnO:Al films having thickness of 300 nm were investigated by XRD. **Figure 1** shows the XRD pattern of ZnO:A thin films deposited at a substrate temperature of 200 °C for alloy target and 300 °C for ceramic target, where the oxygen and argon flow rate were kept at 5.17, 5.19 and 5.23 ml/min and 20, 30, 50 ml/min, respectively. The films exhibited a high degree of preferred orientation, which depends on the various gas flow rates. In this study, all prepared ZnO:Al films exhibit strong diffraction peaks of (002) which is consistent with hexagonal wurzite phase of ZnO. For the films prepared using alloy target, increasing oxygen flow rates from 5.17 ml/min to 5.19 did not change the locations of the measured diffraction peaks but they become more intense. However, further increase in oxygen flow rate to 5.21 ml/min, the intensity of

the peak decreases. For films prepared from ceramic target, it is seen that the peak becomes more intense and sharper with decreasing argon flow rate. This means that the film crystallinity is improved and the grain size of the crystallites becomes larger at a lower argon flow rate. In this study, lower gas flow rate are expected to improve the crystallinity of the film by increasing the moment transfer of sputtered atoms to the film growing on the heated substrate.

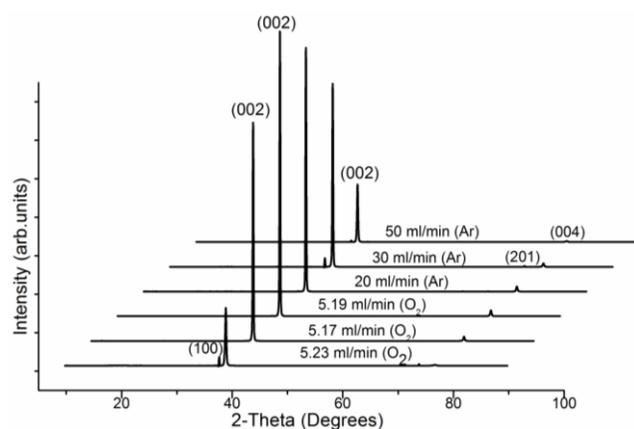


Figure 1: XRD patterns of ZnO:Al thin films deposited under different oxygen and argon gas flow using alloy and ceramic target, respectively. Patterns were analyzed using PANalytical X'Pert Pro powder XRD.

A weak diffraction peak of (201) was observed in films prepared using ceramic and alloy targets at an Ar and oxygen flow rate of 30 ml/min and 5.23 ml/min, respectively, which then disappeared with decrease in Ar flow rate. The diffraction peaks of (100) and (004) were also observed in both films but neither aluminium oxide (Al_2O_3) nor metallic (Zn or Al) phases were observed. This indicates that, the prepared

ZnO:Al films were crystalline exhibit a strong *c*-axis preferred orientation.

3.2 ELECTRICAL PROPERTIES

A comparative films study prepared from ceramic target having resistivity and mobility ranging from 3.421×10^{-3} to $4.023 \times 10^{-4} \Omega\text{cm}$ and 14.08 to 16.53 cm^2/Vs , respectively, the electrical properties of films prepared using alloy target are effectively improved. The films exhibit relatively low resistivity ranging from $(1.588 - 2.908) \times 10^{-4} \Omega\text{cm}$ which is close to those reported elsewhere (Minami *et al.* 1985) and higher mobility ranging from 13.5 to 16 cm^2/Vs . The carrier concentration for films prepared from alloy target ranged from $1.532 \times 10^{21} \text{cm}^{-3}$ to $1.981 \times 10^{21} \text{cm}^{-3}$ while those prepared from ceramic target ranged from $3.08 \times 10^{20} \text{cm}^{-3}$ to $1.33 \times 10^{21} \text{cm}^{-3}$.

Despite the fact that both films having the same thickness $\sim 300 \text{ nm}$ but they have quite different electrical properties as show in Table 1. The good electrical properties of the films prepared from alloy target might be due to the incorporation of Al from the alloy target into zinc in the lattice and thus increasing carrier concentration and mobility of the films. However, with increasing oxygen gas flow into the chamber, lead to the increase in resistivity and decrease mobility and carrier concentration. This observed increase in resistivity with increase in oxygen gas flow rate can be caused by increased oxygen (O) atoms involved in the process of reactive sputtering, oxygen atom combined to metal oxide with metal, leading to the decreased Zn interstitial

atoms. Furthermore, metallic Al atoms might be combined with oxygen atoms to oxides, and thus increasing resistivity and there after decrease in mobility and carrier concentration. Similar results were reported by Liu *et al.* (2010).

resistance and resistivity and higher mobility and carrier concentration have been obtained at a substrate temperature of 200 °C. This demonstrates that DC sputtering from alloy target is better suited for TCO since it can be

Table 1: Properties of notable ZnO:Al films prepared from alloy and ceramic targets, at substrate temperature of 200 °C and 300 °C, respectively, at a sputtering power of 70 W. Thickness of both films was ~300 nm.

Properties	O ₂ (ml/min)	Rs Ω/sq	$\rho \times 10^{-4} \Omega\text{cm}$	$\eta \times 10^{21} \text{cm}^{-3}$	$\mu \text{cm}^2/\text{Vs}$
Alloy (Zn:Al) target	5.15	19.3	3.931	1.75	15.04
	5.17	14.11	2.204	1.98	15.80
	5.19	10.8	2.307	2.98	15.97
	5.21	15.2	2.248	1.92	15.17
	5.23	17.5	2.523	1.93	15.03
Ceramic (ZnO:Al) target	10	46.3	0.974	0.87	14.01
	20	30.7	4.023	0.92	14.18
	30	34.5	9.625	0.90	14.06
	40	38.1	9.801	0.89	13.73
	50	45.3	0.723	0.86	13.47

The same trend was also observed for films prepared using ceramic target, where the resistivity was found to decrease with the decrease of argon gas flow rate. The lowest resistivity of 4.023×10^{-4} was obtained at an argon gas flow rate of 20 ml/min. The conduction mechanism of ZnO:Al films prepared using ceramic target, is affected by argon flow rate. This is due to the variation in grain size, which differs accordingly with argon flow rate (Dong-Joo *et al.* 2004). In this study, the mobility and carrier concentration were found to decrease with increase in argon gas flow rate due to the fact that at increased argon flow rate resulted in stronger collision between the sputtered target atoms with the argon atoms thus reducing kinetic energy of the sputtered atoms. This can hinder their migrating capability on the substrate, resulting in small grain size of the film which also can reduce the mobility of the film. Collectively (from Table 1), the films grown from the alloy targets exhibited much preferable electrical characteristics, whereas lower sheet

easily obtained at low temperature with good electrical properties.

3.3. OPTICAL PROPERTIES

The optical properties were controlled by adjusting Ar gas flow ratio and oxygen flow rate as a mixture of Ar+O₂ gases for ceramic and alloy targets, respectively. The transmittance of the films prepared from both targets was higher than 80 % with oscillatory character due to interference effects in the visible region from 300 to 800 nm with a sharp fall in the transmittance at the absorption edge as shown in panels a and b of **Figure 2**. Plasma frequency shifted to higher wavelength with increase in oxygen flow rate in the mixture of Ar+O₂ gases and Ar flow ratio for films prepared from alloy and ceramic targets, respectively, and showed excellent NIR shielding as can be seen in **Figure 2**. This might be due to zinc adsorption and substitutional doping of an Al³⁺ at the Zn²⁺ site creating one extra free carrier in the process

which occurs at a substrate at low gas flow ratios which leads to the increase in carrier concentration (Sittinger *et al.* 2009, Sittinger *et al.* 2010, Hwang *et al.* 2011). An increased carrier concentration can give increased absorption in the long wavelength region due to free electron gas. Similar results for the films prepared using alloy target were reported

which relates the absorption coefficient (α) and the gap energy (E_g).

$$\alpha h\nu = B(h\nu - E_g)^{1/2} \quad (4)$$

where $h\nu$ is the photon energy, E_g is the optical

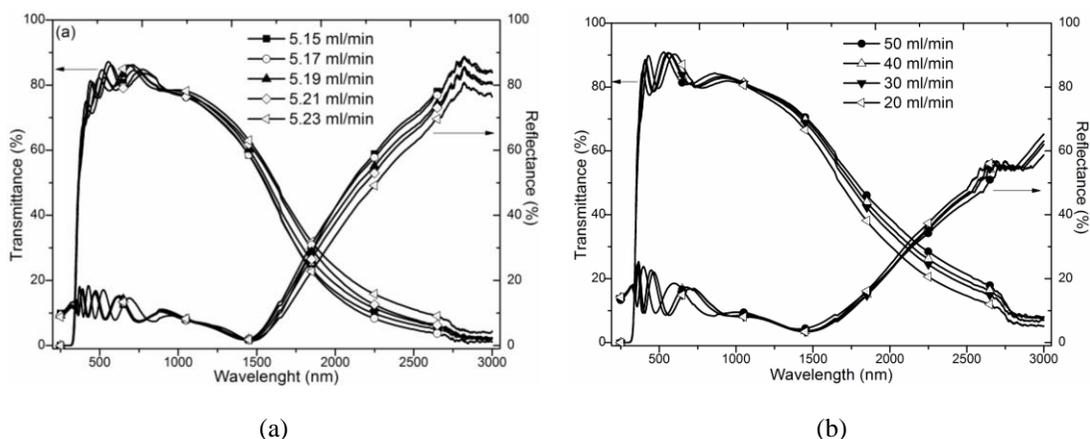


Figure 2. (a) Optical transmittance and reflectance spectra of ZnO:Al films grown at various O₂ flow ratio as a mixture of Ar + O₂ gas at 200 °C (b) Optical transmittance and reflectance spectra of ZnO:Al thin films prepared at different argon gas flow rate.

elsewhere (Theiss 2008, Liu *et al.* 2010, Sittinger *et al.* 2010, Hwang *et al.* 2011). The films from both targets show typical optical characteristics of TCOs whereas they have a transmission window in the 400 – 1500 nm wavelength range. However, the highest average optical transmittance was achieved using ceramic target and was calculated to be ~80.14 %. The difference arises in near normal reflectance in the NIR region where the films prepared from alloy target showed high NIR reflectance, higher than 80%. The optical energy gap is determined from transmittance spectral data using Equation 4,

gap energy for direct allowed transitions and B is the factor depends on the transition probability and is taken as constant within the optical frequency range. The band gap was observed to shift from 3.49 to 3.43 eV with decrease in argon gas flow rate. Films prepared from alloy target the band gap was increased from 3.34 to 3.54 eV with decrease in oxygen gas flow rate. This is possibly due to the Burstein-Moss shift which is attributed to an increase in the carrier concentration as it is seen section 3.2. This increase in carrier concentration blocks the lowest states (filled states) in the conduction band from absorbing the photons (Liu *et al.* 2010)

resulting in widening of the band gap energy. The shift in absorption edge might also be due to the presence of residual compressive stress as reported by Özgür and his co-workers (Özgür *et al.* 2005). The kinks observed at wavelength 870 nm were due to default switching of the detectors of the Spectrophotometer.

The optical constants (refractive index, n and extinction coefficient, k) as obtained by fitting the experimental spectral transmittance data

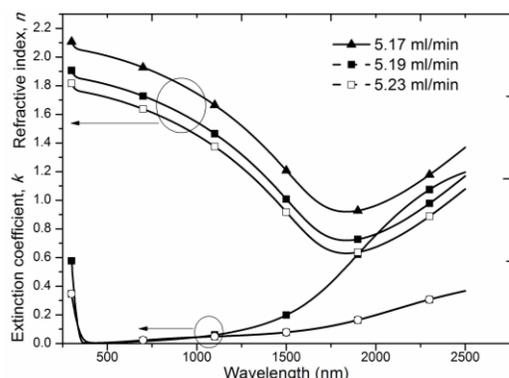


Figure 3. Dependence of refractive indices and extinction coefficients of ZnO:Al films on O₂ flow rates.

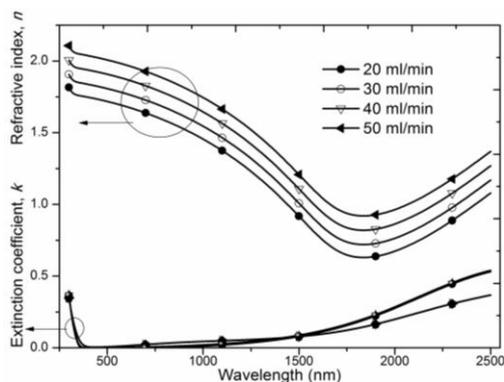


Figure 4. Dependence of refractive indices and extinction coefficients of ZnO:Al films on argon flow rates.

using SCOUT software corroborate with the results of polycrystalline ZnO:Al thin films calculated by other methods indicating excellent fit of the models used. As can be seen from (Figure 3), with variation of the oxygen gas flow rate the refractive index varies as well as the extinction coefficient but in a less pronounced way. It was with the increase of the oxygen flow rate, ZnO:Al thin films tend to be non-stoichiometric and the packing density increases which results in an increase of the refractive index (Jung *et al.* 2003, Al-Hardan *et al.* 2010). The well known that the refractive index is closely related to the density of materials, being lower at lower density. Furthermore, the number of oxygen atoms may be more than the number of zinc atoms and the film tends again to be non-stoichiometrical which exhibited a lower degree of crystallinity as depicted shown in Figure 1, which results in an increase of the refractive index (Jung *et al.* 2003). Similar results were observed for films prepared from ceramic target, refractive indices were found to increase with the increase of argon gas flow ratio as shown in Figure 4. The reason behind the decrease can be attached to the increase in carrier density, which results in the shift of both plasma frequency and the band gap to higher energies, similar to that reported for ITO films (Qiao *et al.* 2006).

In the visible region, refractive index n decreases with wavelength, which correlates with the corresponding increase in transmittance. The obtained values of n agree well with the values obtained using other methods reported elsewhere (Bandyopadhyay *et al.* 2002, Jung *et al.* 2003, Xue *et al.* 2006, Li et al 2008, Li-Ping *et al.* 2012). This is a typical behavior for a semiconductor and thus shows a normal dispersion. The extinction coefficient k as a function of wavelength of the films is almost constant in the visible region for all the samples indicating weak absorption as evidenced by high transmittance in this region. These films exhibit

high extinction coefficient in the plasma edge, suggesting absorption of photons in NIR regions, respectively. However, for both films, the change was small implying little absorption in the visible range, which is consistent with the transmittance spectra results, as shown in **Figure 2**(a and b). The result is in agreement with those reported for ZnO:In (Li-Ping *et al.* 2012).

4.0. CONCLUSION

In the present work ZnO:Al thin films were deposited onto soda lime glass (SGL) slides by reactive and non-reactive DC magnetron sputtering. The effects of target composition (Zn:Al (2% Al) metal alloy and ZnO:Al (2% Al) ceramic targets on optical constants of ZnO:Al thin films were studied. XRD pattern of ZnO:Al films were largely grown along (002) reflection plane under lower oxygen and argon gas flow rate. The deposited ZnO:Al films were highly conductive. However, films with lowest electrical resistivity of 2.04×10^{-4} and highest carrier concentration and mobility of $2.98 \times 10^{21} \text{ cm}^{-3}$ and $15.97 \text{ cm}^2/\text{Vs}$, respectively, were obtained from ZnO:Al films prepared from alloy target. All the films showed more than 80% transparency in the entire visible region. The values of n and k were found to vary significantly with deposition parameters, whereby for different samples ranged from 1.59 to 2.2 and 0.00013 to 1.2194 respectively. Nevertheless, the obtained values are in range of the values reported for ZnO:Al films. Despite similar optical constants and being in range with those reported in literatures, these results confirm that the films with good optical properties can be achieved using metal alloy target, since good electrical together with structural properties were obtained using metal alloy target. This demonstrate that ZnO:Al thin films prepared from metal alloy can be used as an appropriate

TCO material in CIGS solar cells since they are deposited at lower temperature $200 \text{ }^\circ\text{C}$ recommended for CIGS solar cells.

ACKNOWLEDGEMENTS

The University of Dodoma and Solar Energy Group, Physics Department, University of Dar es Salaam, are greatly acknowledged for full financial assistance to the current work.

REFERENCES

- Alnajjar AA 2012 ZnO:Al grown by sputtering from two different target sources: A comparison study. *Advances in Condensed Matter Physics* **2012**: 1-8.
- Bandyopadhyay S, Paul GK, Sen SK 2002 Study of optical properties of some Sol-Gel derived films of ZnO. *Solar Energy Materials and Solar Cells* **71**: 103–113.
- Beyer W, Hüpkes J and Stiebig H 2007 Transparent conducting oxide films for thin film silicon photovoltaic. *Thin Solid Films* **516**: 147–154.
- Dong-Joo K, Kang-II P, Byung-Sub K and Su-Ho L 2004 Argon gas pressure and substrate temperature dependences of ZnO:Al film by magnetron sputtering. *J. of the Korean Physical Society* **45(1)**: 206-210.
- Ehrmann N and Reineke-Koch R 2010 Ellipsometric studies on ZnO:Al thin films: Refinement of dispersion theories *Thin Solid Films* **519**: 1475-1485.
- Fernández S and Naranjo FB 2010 Optimization of aluminum-doped zinc oxide films deposited at low temperature by radio-frequency sputtering on flexible substrates

- for solar cell applications *Solar Energy Materials and Solar Cells* **94**: 157–163.
- Granqvist CG 2007 Transparent conductors as solar energy materials: A panoramic review. *Solar Energy Materials and Solar Cells* **91**: 1529–1598.
- Hamberg I and Granqvist CG 1986 Evaporated Sn doped In_2O_3 films: Basic optical properties and applications to energy-efficient windows *J. of Applied Physics* **60**: R123-R160.
- Hong RJ, Jiang X, Szyszka B, Sittinger V and Pflug A 2003 Studies on ZnO:Al thin films deposited by in-line reactive mid-frequency magnetron sputtering. *Applied Surface Science* **207**: 341-350.
- Huang CH, Cheng HL, Chang WE and Wong MS 2011 Comprehensive characterization of DC sputtered AZO films for CIGS photovoltaics. *J. of the Electrochemical Societ.* **158** (5): H510-H515.
- Hwang D, Ahn J, Hui K, Hui KN and Son Y 2011 Effects of oxygen partial pressure contents on the properties of Al-doped ZnO thin films prepared by RF sputtering. *J. of Ceramic Processing Research* **12** (2): 150-154.
- Jung YK, Seo JK, Lee DW, Jeo DY 2003 Influence of DC magnetron sputtering parameters on the properties of amorphous indium zinc oxide Thin Film. *Thin Solid Films* **445**: 63-71.
- Kim S, Lee W and Lee C 2007 Influence of ZnO buffer layer thickness on electrical and optical properties of GZO thin films deposited on polymer substrates. *Materials Science and Tech.* **23** (3): 303–306.
- Kuo CC, Liu CC, He SC, Chang JT and He JL 2012 Effects of additional oxygen flow on the optical and electrical properties of ion beam sputtering deposited molybdenum-doped zinc oxide layer *J. of Nanomaterials* **2012**: 562701 1-8.
- Liu H, Avrutin V, Izyumskaya N, Özgür Ü and Morkoç H 2010 Review: Transparent conducting oxides for electrode applications in light emitting and absorbing devices. *Superlattices and Microstructures* **48**:458–484.
- Li LN, Zhao Y, Chen XL, Sun J and Zhang, XD 2012 Effects of oxygen flux on the Aluminum doped Zinc Oxide thin films by direct current magnetron sputtering. *Physics Procedia* **32**: 687 – 695.
- Li QH, Zhu D, Liu W, Liu Y and Ma XC 2008 Optical properties of Al-doped ZnO thin films by Ellipsometry. *Applied Surface Science* **254**: 2922-2926.
- Li-Ping P, Liang F, Wei-Dong W, Xue-Min W and Li L 2012 The effects of post thermal annealing on the optical parameters of Indium-doped ZnO thin films. *Chinese Physics. B.* **21** (4): 047305 1-5.
- May C, Menner R, Strumpfel J, Oertel M and Sprecher B 2003 Deposition of TCO films by reactive magnetron sputtering from metallic Zn:Al alloy targets. *Surface and Coatings Tech.* **169-170**: 512-516.
- Minami T, Nanto H and Takata S 1985 Optical properties of Aluminium doped Zinc Oxide thin films prepared by RF magnetron sputtering. *Japanese J. of Applied Physics* **24** (8): L605-L607.
- Özgür Ü, Alivov YI, Liu C, Teke A, Reshchikov MA, Doğan S, Avrutin V, Cho SJ and Morkoç H 2005 A comprehensive review of ZnO materials and devices. *J. of Applied Physics* **98**: 041301 1-123.
- Qiao Z, Agashe C and Mergel D 2006 Dielectric modelling of transmittance spectra of thin ZnO:Al films. *Thin Solid Films* **496**: 520 – 525.
- Reddy RS, Sreedhar A, Reddy SA, Uthanna S 2012 Effect of film thickness on the structural morphological and optical properties of nanocrystalline ZnO films

- formed by RF magnetron sputtering. *Advanced Materials Letters* **3** (3): 239-245.
- Schaefer C, Brave G and Szczyrbowski C 1997 Low emissivity coatings on architectural glass. *Surface and Coating Tech.* **93**: 37-45.
- Sittinger V, Dewald W, Werner W and Szyszka B 2009 Comparison of different ceramic Al-doped ZnO target materials. *Photovoltaics International* **6**: 101-108.
- Sittinger V, Dewald W, Werner W and Szyszka B 2010 Transparent conducting oxide deposition techniques for thin-film photovoltaics. *Photovoltaics International* **6**: 108-115.
- Sittinger V, Ruske F, Pflug A, Dewald W, Szyszka B and Dittmar G 2010 Optical on-line monitoring for the long-term stabilization of a reactive mid frequency sputtering process of Al-Doped Zinc Oxide films. *Thin Solid Films* **518**: 3115–3118.
- Suchea M, Christoulakis S, Katsarakis N, Kitsopoulos T and Kiriakidis G 2007 Comparative study of Zinc Oxide and Aluminium Doped Zinc Oxide transparent thin films grown by direct current magnetron sputtering. *Thin Solid Films* **515**: 6562-6566
- Theiss, W. (2008). Hard and soft copy for optical spectroscopy, Aachen, Germany. www.mtheiss.com.
- Wang H, Xu J, Ren M and Yang L 2009 Room temperature deposition and properties of ZnO:Al thin films by nonreactive DC magnetron sputtering. *J. of material science: Materials in Electronics.* **19**: 1135-1139.
- Xue SW, Zu X T, Zheng WG, Deng HX and Xiang X 2006 Effects of Al doping concentration on the optical parameters of ZnO:Al thin films by Sol-gel technique. *Physica B: Condensed Matter.* **381** (1-2): 209-213.
- Al-Hardan NH, Abdullah MJ, Abdul Aziz A, Ahmad H and Rashid M 2010 The effect of oxygen ratio on the crystallography and optical emission properties of reactive RF sputtered ZnO films. *Physica B: Physics of Condensed Matter.* **405** (4): 108-1085.